

Weak magnetoresistance of disordered heavy fermion systems

A. Chattopadhyay¹, M. Jarrell¹, H. R. Krishnamurthy^{1,2}, H. K. Ng³, J. Sarrao⁴ and Z. Fisk⁵

¹ *Department of Physics, University of Cincinnati
Cincinnati, Ohio 45221*

² *Department of Physics, Indian Institute of Science
Bangalore 560012, India*

³ *Department of Physics and Center for Materials Research and Technology
Florida State University, Tallahassee, FL 32306-4350*

⁴ *MS K764 / Group MST-10, Los Alamos National Laboratory
Los Alamos, NM 87545*

⁵ *National High Magnetic Field Laboratory
Florida State University, Tallahassee, FL 32306
(February 7, 2008)*

We compare the magnetoresistance of $\text{UCu}_{3.5}\text{Pd}_{1.5}$ with calculations done within the disordered heavy fermion framework of Miranda et al. using a phenomenological spectral function for the Anderson model, calibrated against Bethe ansatz and quantum Monte Carlo results. Both in experiment and theory, we find a weak negative magnetoresistance. In contrast, thermodynamic quantities have a strong field dependence. Using qualitative arguments broad distribution of Kondo scales, we explain the different field dependence of susceptibility and resistivity.

75.30.Mb, 71.27.+a, 75.20.Hr

Introduction. In the past few years, transport and thermodynamic measurements on several heavy fermion systems have suggested the possibility of a non-fermi liquid ground state. The violation of fermi liquid theory is evident in the measured linear resistivity at low T , a logarithmic low temperature divergence of the susceptibility and the specific heat coefficient, an optical conductivity with a low frequency pseudogap and a linear transport scattering rate at low frequencies [1–3]. Several theoretical models have been proposed to explain this breakdown of the fermi liquid paradigm. They include the multi-channel Kondo impurity and lattice models [4], quantum fluctuations near a quantum critical point [5,6], competition between local charge and spin fluctuations in infinite dimensions [7], and the disordered Kondo model with a disorder driven distributions of Kondo scales [8,9].

In this paper we discuss the properties of the disordered Kondo model in a magnetic field. The experimental systems we focus on for comparison are the U-based compounds $\text{Y}_{1-x}\text{U}_x\text{Pd}_3$ and $\text{UCu}_{3.5}\text{Pd}_{1.5}$ [1,5] where there is some consensus that the non-Fermi liquid ground states are disorder induced. In a magnetic field both of these systems display a very weak negative magnetoresistance, but a large change in susceptibility [5,8]. This is in sharp contrast to canonical dilute magnetic alloys with a single small Kondo scale ($\text{La}_{1-x}\text{Ce}_x\text{B}_6$; $T_K \approx 1\text{K}$) where one usually sees a strong negative magnetoresistance ($\Delta\rho(H)/\rho(0) \approx 90\%$ at fields $\sim 2 - 3T$) with a comparable change in the thermodynamic response. We address these two issues in this paper. First, we discuss the calculation of magnetoresistance within the disordered Kondo model, compare the theoretical results with new experimental data (reported here for the first time) and present a qualitative argument for the

observed weak field dependence of $\rho(H)$ at finite temperatures. Second, we present an explanation for the difference in the field dependence of transport and thermodynamic quantities at $T = 0$.

Formalism The theoretical calculations reported in this paper use an extension to finite magnetic fields of the formalism developed in a previous paper [10], where the optical conductivity for a *dilute* collection of Kondo impurities in a disordered host, such as in $\text{Y}_{1-x}\text{U}_x\text{Pd}_3$, was calculated assuming a distribution of Kondo temperatures. However, we believe that the leading dependence (at T, H much smaller than the bulk T_K^0) should apply to concentrated systems like $\text{UCu}_{3.5}\text{Pd}_{1.5}$ as well.

The dilute system may be modeled in terms of symmetric nondegenerate Anderson impurities. In the absence of a magnetic field, the impurity f-density of states has a sharp resonance at the Fermi level, giving significant impurity contributions to the transport, specific heat and magnetic susceptibility. Most of the heavy fermion systems we consider exhibit strong $L-S$ coupling. Hence the dominant effect of the B-field is to Zeeman couple to the f-spins. For a given T_K , the magnetic field splits the up and down f-spins, giving rise to a different spectral function for each spin species. Concentrating on the Kondo limit of the Anderson model ($n_f \approx 1$), the phenomenological expression [10–12] for the Kondo resonance can be extended to include the magnetic field effects as

$$A_{f\uparrow}(\omega) = \frac{1}{\pi\Delta} \text{Re} \left[\frac{i\Gamma_K}{(\omega - \alpha H + i\sqrt{\Gamma_K^2 + \beta^2 + \gamma^2})} \right]^{1/2}. \quad (1)$$

Here α and β are assumed to be functions of magnetic field but independent of temperature, $\Gamma_K = (\pi/2)^2 T_K$,

Δ is the f-d hybridization energy and $\gamma(T/T_K)$ is a universal function that captures the temperature dependence of the spectrum [10]. The Zeeman-like term α reflects the shift in the spectral peak with respect to the Fermi energy. Particle-hole symmetry implies that $A_{f,\uparrow}(\omega) = A_{f,\downarrow}(-\omega)$.

At $T = 0$, the impurity magnetization is given by (in units of $\frac{g\mu_B}{2}$)

$$m(H/T_K) = \int_{-\infty}^0 d\omega [A_{f\uparrow}(\omega, H/T_K) - A_{f\downarrow}(\omega, H/T_K)] . \quad (2)$$

When $H/T_K \ll 1$, it is reasonable to assume that to leading order $\alpha(\frac{H}{T_K}) \approx \alpha_0$ and $\beta(\frac{H}{T_K}) \approx \beta_0 \frac{H^2}{T_K^2}$ (where the prefactors α_0 and β_0 are now constants). Under these assumptions, when eq.(2) is expanded up to $O(\frac{H}{T_K})^3$, we have

$$m(H/T_K) \approx \frac{4T_K}{\pi\Delta} \left[\frac{\alpha_0}{2} \left(\frac{H}{T_K} \right) - \left(\frac{\alpha_0^3}{16} + \frac{\alpha_0\beta_0}{8} \right) \left(\frac{H}{T_K} \right)^3 \right] . \quad (3)$$

By comparing the right hand side of eq.(3) to the Bethe ansatz expression for the low-field impurity magnetization in powers of $\frac{H}{T_K}$ [13] we get the low H values of α, β .

In principle the Bethe ansatz series (which is valid for $H \leq T_K$) can be reproduced only by using an infinite number of coefficients in our spectral function, but α_0 and β_0 capture the dominant low field effects. This is confirmed at a low $T \neq 0$ by calculating the f-spectra of the symmetric Anderson model in a finite field by Quantum Monte Carlo (QMC). The numerical analytic continuation is done using maximum entropy method (MEM) [14,15], with the perturbation theory spectrum as the high temperature default. Using the MEM results, the expression for the spectral function can be calibrated and $\alpha(H/T_K)$ and $\beta(H/T_K)$ determined over a wide range of field values. The results are shown in Fig. 1. The fits tend to be reasonable until the frequency reaches the charge transfer peak.

In the dilute limit, the impurities can be assumed to be independent scatterers and the universal single impurity spectral function (Eq.1) can be disorder averaged to calculate dynamical quantities. The Hilbert transform of $A_f(\omega, T_K)$ for each spin species then gives the average impurity t-matrix

$$t_f(z) = \int dT_K P(T_K) \int d\omega \frac{V^2 A_f(\omega, T_K)}{z - \omega} , \quad (4)$$

where V is the f-d hybridization. For the phenomenological spread of Kondo scales, we assume the form

$$P(T_K) = \frac{0.01}{e^{(T_K - T_K^0)} + 1} . \quad (5)$$

This distribution is not based on microscopics; it simply satisfies the experimental criterion of constancy at low T_K and looks qualitatively similar to the $P(T_K)$ for $\text{UCu}_{5-x}\text{Pd}_x$ [8]. Following Miranda, et al. [9] one uses the dynamical mean-field approximation [16], which becomes exact in the limit of infinite dimensions, to calculate the lattice self energy for a concentration x of substitutional Kondo impurities as

$$\Sigma(\omega) = \frac{xt_f(\omega)}{1 + xt_f(\omega)\mathcal{G}(\omega)} , \quad (6)$$

where $\mathcal{G}(\omega)$ describes the average effective medium of the impurity. It is related to the average local greens function G

$$G(\omega) = \int d\epsilon \frac{N(\epsilon)}{\omega - \epsilon + \mu - \Sigma(\omega)} , \quad (7)$$

through the relation

$$\mathcal{G}^{-1} = G^{-1} + \Sigma , \quad (8)$$

where $N(\epsilon) = \frac{1}{t^*\sqrt{\pi}} e^{-\epsilon^2/t^{*2}}$ and we set $t^* = 10,000K$ to establish a unit of energy and temperature. The solutions of Eqns. 4–8 then give the full self energy.

The knowledge of this self energy enables one to calculate physical quantities [17] like transport coefficients and the optical conductivity. In this paper we concentrate on the magnetoresistance $\rho(H)$. It is measured in units of $\rho_0 = 2\hbar/e^2\pi a$, which (with $\hbar/e^2 \approx 2.6 \cdot 10^4\Omega$) varies between $10^2 \dots 10^3 [\mu\Omega\text{cm}]$, depending on the lattice constant a .

Results Figs.2a and 3b show some new experimental data for the magnetoresistance of $\text{UCu}_{3.5}\text{Pd}_{1.5}$ and Figs. 2b and 3a the calculated values. The experimental measurements were made on a polycrystalline sample of size 3.0 mm by 0.47 mm by 0.52 mm. The sample was grown by arc melting the constituents and sealed in quartz tube and annealed for 10 days at 800°C. The resistivity was measured using a 4 probe technique in a 12 Tesla Oxford superconducting magnet. A constant current of 10 mA was used for all the measurements. To eliminate the possibility of any heating effect, the current was reduced to 5 mA for one of the temperature scans. No discernible difference was observed. The calculations were done assuming $T_K^0 = 100K$ which is roughly the bulk Kondo temperature in $\text{UCu}_{3.5}\text{Pd}_{1.5}$.

As one can see, there is strong qualitative resemblance between the experimental and theoretical curves. The general trend is that at very low T , there is a negative magnetoresistance even at the lowest fields. As one increases T , $\rho(H)$ is relatively constant up to field values comparable to the temperature, beyond which there is a downturn. From Fig. 2, we see that there is almost quantitative agreement at 4K. At 20K, we are at temperatures comparable to T_K^0 and the self-consistent modifications to $P(T_K)$ presumably are significant for the

lattice. The qualitative agreement is still there in that $\rho(H, T = 20K)$ is nearly a constant over $12T$.

This interplay of magnetic field and temperature can be understood as follows. Let us look at the temperature dependence of the susceptibility and resistivity for a given Kondo scale. In the case of $\chi(T/T_K)$, the $T = 0$ value is given by $\frac{1}{T_K}$, which means that lowering the Kondo temperature will result in an enhancement of $\chi(T = 0)$. A similar argument holds for C_V/T as well. So in a system with a distribution of Kondo scales, the low T thermodynamics (χ, C_V) are dominated by the sites with the lowest T_K values. The case of resistivity is different since for any fixed T_K , $\rho(T = 0)$ is pinned at the unitarity limit. Hence lowering of the Kondo scales will end up "squeezing" the "local Fermi liquid" regime in temperature (where $\delta\rho(T/T_K)$ scales like $1 - (T/T_K)^2$). As a result, the dominant (but by no means exclusive) contribution to transport at low T comes from sites with high Kondo scales, particularly $T_K \gtrsim T$.

Now, in the presence of a broad distribution $P(T_K)$, consider a temperature T and a field $H \ll T$. For any site with $T_K \lesssim H$ the Kondo singlet will be broken. Since these low T_K sites are the ones dominating the thermodynamics, any finite magnetic field will have an appreciable effect on χ . On the other hand, a majority of the sites that affect transport at T are unaware of this low field. The field dependence of the resistivity shows up only when $H \approx T$, where the system acquires an increasing number of free spins by breaking the relevant Kondo singlets. This gives rise to a weak negative magnetoresistance which is confirmed by the magnetotransport measurements on $\text{UCu}_{3.5}\text{Pd}_{1.5}$. The broadness of $P(T_K)$ in this case is crucial for $\Delta\rho(H)/\rho(0)$ to be weak compared to $\text{La}_{1-x}\text{Ce}_x\text{B}_6$, for instance. This is because even when $H \approx T$, there are a significant number of sites that have Kondo scales $T_K \gg T, H$ that contribute to the resistivity through nearly unitary scattering.

A natural extension of this argument would suggest a gentle initial upturn in the resistivity data at $H \approx T$ if there is an initial upturn in $P(T_K)$. This trend is noticed in the data on $\text{UCu}_{3.5}\text{Pd}_{1.5}$ [Fig. 2(a), 3(b)], indicating that the distribution of Kondo scales in the real sample is not really flat at the low T_K end but has an upward slope. We have calculated $\rho(H, T)$ for such a distribution and confirmed this behaviour.

We have also re-calculated χ within our framework (earlier calculations were done by Bernal et al. [8] and Miranda et al. [9]) to illustrate the difference with resistivity in a field and show the results in Fig. 3c. Here, for consistency with experiments, $\chi(T)$ is defined as $\overline{m(H, T)}/H$ where $\overline{\quad}$ denotes disorder averaging. The resistivity responds to the magnetic field much more weakly than χ does. At $T = 1K$, ρ changes by 3% when a 6 Tesla field is applied to the system; χ changes by 24% over the same range. This is in qualitative agreement with the experiments on $\text{Y}_{1-x}\text{U}_x\text{Pd}_3$ and $\text{UCu}_{3.5}\text{Pd}_{1.5}$.

The significantly different field dependence of ρ and χ can be understood as follows from the $T = 0$ Bethe ansatz expression relating the magnetization to the resistivity in the single impurity Kondo model:

$$R_{\text{imp}}(H/T_K) = R_{\text{imp}}(0) \cos^2 \left[\frac{\pi}{2} f(x) \right]. \quad (9)$$

Here $x \equiv \frac{g\mu_B H}{k_B T_K} = \frac{\tilde{H}}{T_K}$ and $f(x) = \frac{2}{g\mu_B} m(x)$. Disorder averaging, for simplicity, over a rectangular distribution of T_K upto T_K^0 , one gets

$$\frac{\overline{R_{\text{imp}}(H)}}{R_{\text{imp}}(0)} \sim \frac{\tilde{H}}{T_K^0} \int_{\frac{\tilde{H}}{T_K^0}}^{\infty} \cos^2 \left[\frac{\pi}{2} f(x) \right] \frac{1}{x^2} dx \quad (10)$$

$$\overline{\chi_{\text{imp}}(H)} \sim \int_{\frac{\tilde{H}}{T_K^0}}^{\infty} f'(x) \frac{1}{x} dx. \quad (11)$$

For large $\tilde{H}$, the integrals are dominated by large x where the integrands scale like $\frac{\pi^2}{16} \frac{1}{(x \ln(x))^2}$ and $\frac{1}{2} \frac{1}{(x \ln(x))^2}$ respectively. So the integrals are comparable for large $\frac{\tilde{H}}{T_K^0}$, implying that $\overline{\chi_{\text{imp}}}$ falls off faster than $\overline{R_{\text{imp}}(H)}$. For small $\frac{\tilde{H}}{T_K^0}$, $\overline{\chi_{\text{imp}}}$ has a log divergence from the small x region. The resistivity integral has a $\frac{T_K^0}{H}$ divergence as well, but it gets balanced out by the prefactor. Hence, $\overline{R_{\text{imp}}(H)}$ has a weaker dependence on field compared to $\overline{\chi_{\text{imp}}(H)}$ for both large and small values of $\frac{\tilde{H}}{T_K^0}$.

Conclusion. We have presented calculations of magnetoresistance within the disordered Kondo scenario and new experimental data for the magnetoresistance in $\text{UCu}_{3.5}\text{Pd}_{1.5}$ at a variety of temperatures and find the results to be consistent. The weak magnetoresistance of this system at finite temperature has been qualitatively explained by examining the interplay of field and temperature in the presence of a wide distribution of Kondo scales. Finally, we have addressed the stronger field dependence of susceptibility as compared to transport and presented a calculation at $T = 0$ to explain this.

We are thankful to V. Dobrosavljević for motivating this problem. We would also like to acknowledge useful discussions with M. Hettler, M. Ma, D. E. MacLaughlin, Anirvan Sengupta and Q. Si.

This work was supported by NSF grants DMR-9406678 and DMR-9357199.

-
- [1] For a recent review, see M.B. Maple *et al.*, J. Low Temp. Phys. **99**, 223 (1995), and references cited therein.
 - [2] L. Degiorgi, H.R. Ott, and F. Hulliger, Phys. Rev. B **52**, 42 (1995); L. Degiorgi and H.R. Ott, J. Phys.: Cond.

- Matter **8**, 9901(1996); and L.Degiori *et al.*, Phys. Rev. B **54**, 6065 (1996).
- [3] H. v. Löhneysen *et al.*, Phys. Rev. Lett. **72**, 3262 (1994).
- [4] a) P. Nozières and A. Blandin, J. Phys. (Paris) **41**, 193 (1980); b) D. L. Cox, Phys. Rev. Lett. **59**, 1240 (1987); c) Physica B **186-188**, 312 (1993).
- [5] B. Andraka and A. M. Tsvetik, Phys. Rev. Lett. **67**, 2886 (1991).
- [6] M. A. Continentino, Phys. Rev. B **47**, 11587 (1993); A. J. Millis, Phys. Rev. B **48**, 7183 (1993); A. M. Tsvetik and M. Reizer, Phys. Rev. B **48**, 9887 (1993).
- [7] Q. Si, J.Phys. :Cond. Matter **8**, 9953(1996) and references therein.
- [8] O. O. Bernal *et al.*, Phys. Rev. Lett. **75**, 2023 (1995).
- [9] E. Miranda, V. Dobrosavljević and G. Kotliar, Phys. Rev. Lett. **78**, 290 (1997).
- [10] A. Chattopadhyay and M. Jarrell, Phys. Rev. B **56**, R2920 (1997).
- [11] S. Doniach and M. Sunjic, J.Phys.C **3**, 285 (1970); H. O. Frota and L. N. Oliveira, Phys. Rev. B **33**, 7871 (1986).
- [12] H. R. Krishna-murthy, J. W. Wilkins and K. G. Wilson, Phys. Rev. B **21**, 1003 (1980); **21**, 1044 (1980).
- [13] N. Andrei *et al.*, Rev. Mod. Phys. **55**, 331 (1983); A. M. Tsvetik and P. B. Wiegmann, Adv. Phys. **32**, 453 (1983).
- [14] R.N. Silver *et al.*, Phys. Rev. Lett. **65**, 496 (1990).
- [15] For a review of the Maximum Entropy method of analytic continuation, see M. Jarrell, J.E. Gubernatis, Physics Reports Vol. **269** #3, (May, 1996).
- [16] W. Metzner and D Vollhardt, Phys. Rev. Lett. **62**, 324 (1989).
- [17] Th. Pruschke, M. Jarrell and J.K. Freericks, Advances in Physics **44**, 187-210 (March/April 1995).

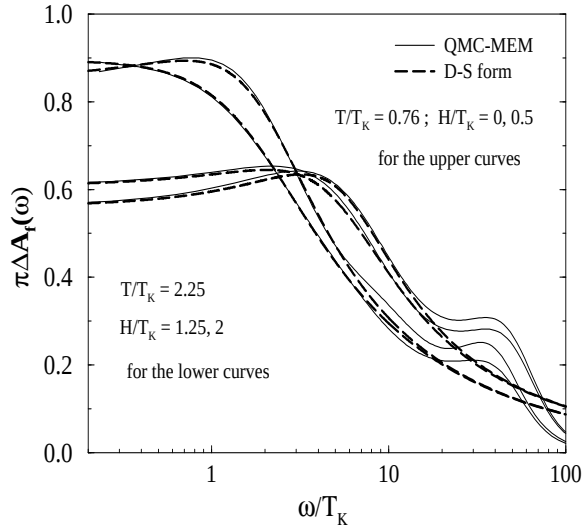


FIG. 1. Spectral function for the up-spin f-electron in the Kondo limit of the Anderson model for different T/T_K and H/T_K values. The dashed lines are the result of the extended Doniach-Sunjic function. The solid lines are the QMC/MEM results. The fit is very reasonable until the charge transfer physics becomes important.

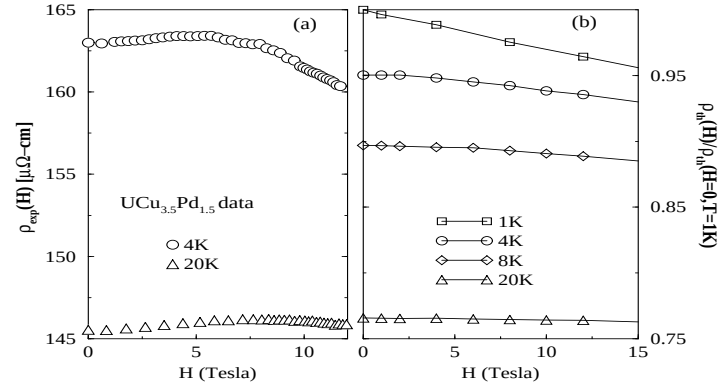


FIG. 2. Magnetic field dependence of the resistivity. Both the experimental measurements (a) on $UCu_{3.5}Pd_{1.5}$ and theoretical plots (b) are shown. The qualitative agreement is quite reasonable. The magnetoresistance becomes negative at field values comparable to the temperature. This is because transport at a given T is dominated by sites that have $T_K \approx T$ or higher. As a result, at any given T the resistivity is unaware of the field until H suppresses the relevant T_K .

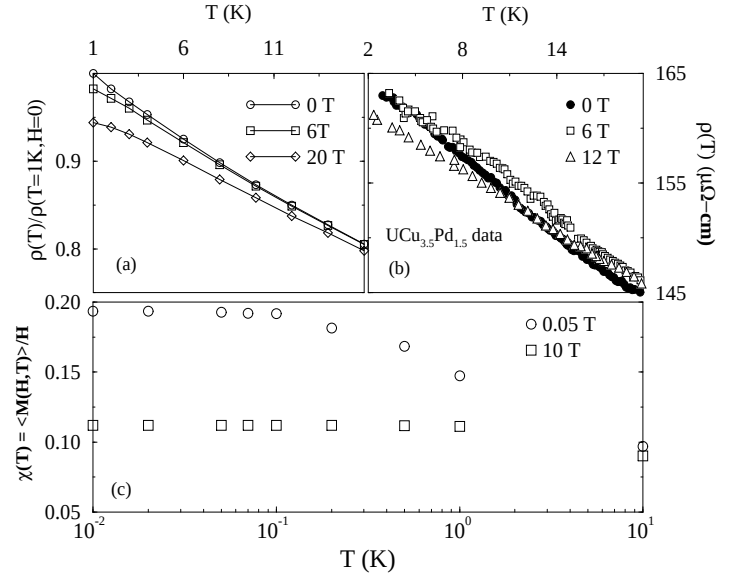


FIG. 3. Resistivity and impurity spin susceptibility within the disordered Kondo model. The susceptibility shown is normalized with its value at $0.01K, 0.05$ Tesla. One notices a far more pronounced effect of magnetic field on $\chi(T)$ at low temperatures, compared to $\rho(T)$. For instance, at $T = 1K$, ρ is estimated to change by 3% over $6T$; χ changes by 24% over the same field value.